

# Development of Ultra-Carbon Steel Prepared by Mechanical Alloying and Subsequent Hot Pressing

Nurul Taufiqu Rochman<sup>1</sup> and H. Sueyoshi<sup>2</sup>

**Abstract**—It is known that the most effective way to improve mechanical properties of steels is by microstructural refinement. Iron and graphite powders mixture with hypo-eutectoid composition were mechanically alloyed (MAed) and subsequently hot pressed (HPed) to provide steels with fine structure. Mechanical Alloying (MA) was carried out using a planetary ball mill for 100, 200 and 300 h, while HP at 41 MPa at various temperatures: 610°C (below), 730°C (near) and 800°C (above the eutectoid transformation point  $A_1$ ). The mechanically alloyed (MAed) powders were characterized by X-ray diffraction (XRD), differential thermal analysis (DTA) and scanning electron microscopy (SEM). While, the HPed compacts were characterized by SEM, Vickers hardness and tensile test. During MA, refinement of crystallite, formations of super-saturated iron solid solution and Fe/C amorphous phase occurred first. With further MA time, these phases might begin to transform to more stable phases such as carbides. In the case of HP at 610°C (below  $A_1$ ), very fine cementites were precipitated in fine ferrite grain with sub-micron meter in the size. However, the mechanical properties cannot be attained because of low sinterability. At 730°C (near  $A_1$ ), the strength reaches the maximum value. With further temperature increase (at 800°C), the sintering progressed well and the coarsening occurred, resulting the decrease in strength. However, the fracture strain increased significantly. The steels obtained in the present study had mechanical properties comparable to those of standard (JIS) steels through the well established heat treatment such as normalizing and thermal refining.

**Keywords**—Mechanical alloying, Ultra-carbon steel, Fine grain ferrite, Fine cementite, Hhot pressing, Heat treatment.

## I. INTRODUCTION

It is well known that mechanical properties of steels such as strength and toughness usually can be improved by grain refinement through thermal refining and addition of alloying elements. However, the grain refinement through thermal refining has a limitation up to only several ten micrometers. On the other hand, in ecomaterial perspective, the addition of alloying elements (such as special elements that become trumped elements etc.) is not desirable due to the problem in recycling process and resource depletion.

Recently, mechanical alloying (MA) was utilized to produce non-equilibrium phases such as amorphous [1],

[2], super-saturated solid solution [2] and nano-crystalline phases [3], [4]. There were reported [5], [6], [7], [8] that these phases also could be obtained in hyper-eutectoid Fe-C systems. The alloying mechanism during MA also had been discussed [8], [9]. During MA, amorphous Fe/C phase and super-saturated iron solid solution transform to metastable carbides such as  $Fe_3C$  and  $Fe_7C_3$  [9], [10], [11], [12].

It is supposed that if the MAed Fe-C powders were consolidated, very fine-grained carbon steels could be attained. Referring to [7], [8] had succeeded to produce Fe-high C system hard alloys from the MAed powders.

In order to make a comparative study, in the present study hypo-eutectoid Fe-C powders were MA-HPed and their mechanical properties were then compared with the standard (JIS) carbon steels through the well-established heat treatment.

## II. EXPERIMENTAL PROCEDURE

Elemental powders of iron (99.5 mass %, 5  $\mu m$ ) and graphite (99.9 mass %, <78  $\mu m$ ) with hypo-eutectoid composition (Fe-0.4 mass % C and Fe-0.6 mass % C) were put into a cylindrical pot (SKD, 450  $cm^3$ ) under an argon atmosphere with two types of stainless balls (SUS 304,  $\mu 12$  mm:  $\mu 7$  mm = 1:1). The ball-to-powder mass ratio was 8:1. MA was carried out at 120 rpm for 100, 200 and 300 h by using a planetary ball mill (PM400, Retsch Industry Inc.). The MAed powders were characterized by X-ray diffraction analysis (XRD), scanning electron microscopy (SEM) and differential thermal analysis (TG-DTA). TG-DTA was performed under argon atmosphere with heating rate of 0.33  $^\circ C/s$ . After MA for 200 and 300 h, the Fe/C alloying powders were HPed at various temperatures (A: below (610°C), B: near (730°C) and C: above (800°C) the eutectoid transformation point  $A_1$ ) at 41 MPa under nitrogen gas atmosphere. The HPed compacts were examined by tensile test at a crosshead speed on 0.5 mm/min, microstructural observation by using SEM and Vickers hardness measurement.

## III. RESULT AND DISCUSSION

Figure 1 shows SEM images of as-received iron and graphite powders. While Figure 2 shows Fe-0.4C and Fe-0.6C powders mixtures MAed for 300 h. The morphology of graphite powders before MA is irregular. While, iron powders is almost spherical (see Figure 1). As shown, after MA for 300 h, the extremely deformed powder particles are observed. The relatively coarsened particles are

Manuscript received August 31, 2006; revised May 22, 2007

<sup>1</sup> Nurul Taufiqu R. is with Research Center for Physics, Indonesian Institute of Sciences, INDONESIA

<sup>2</sup> H. Sueyoshi is with Department of Nano Structured and Advanced Materials, Kagoshima University, JAPAN

the aggregates of very fine particles that form due to the repeated forging, work-hardening, fracture and cold-welding during MA. There is no significant change between the morphology of the MAed Fe-0.6C and Fe-0.4C powders mixtures.

Figure 3 shows XRD patterns of Fe-0.6C powders MAed for various time. The XRD peak of graphite does not appear because of its small amount in the mixed powders. The iron peaks broaden and their intensities decrease as the MA time increases up to 200 h. Also their positions shift to the lower angle. However, the intensity of Fe (110) peak increases again when the MA time is 300 h. This indicates that the refinement of crystallite and amorphization take place first [5], [12]. Also, many carbon atoms dissolve into the iron lattice to form super-saturated solid solution. When the MA time exceeds 200 h, however, only the intensity of a peak at Fe (110) position increased significantly. Referring to [9] reported

that during MA of Fe-C system,  $\alpha$ Fe and graphite transformed to  $\text{Fe}_3\text{C}$  through amorphous Fe/C and  $\text{Fe}_7\text{C}_3$ . Therefore, this new peak might be a kind of carbide. However, we still could not find others peaks in this profile.

Figure 4 shows the changes in the carbon content calculated from the iron lattice parameter using an equation proposed by [13] as a function of MA time. The carbon content increases with the increase of MA time up to 200 h and then decreases with further MA time. The highest carbon content (0.064 mass%) obtained corresponds with the broadest iron peaks for 200 h (see Figure 3). The decrease in carbon content shows that the solubility of carbon into the iron lattice has a limit and with further MA time, the super-saturated iron solid solution and amorphous Fe/C tend to transform to another phase, such as carbide  $\text{Fe}_7\text{C}_3$  or  $\text{Fe}_3\text{C}$  as mentioned by [9].

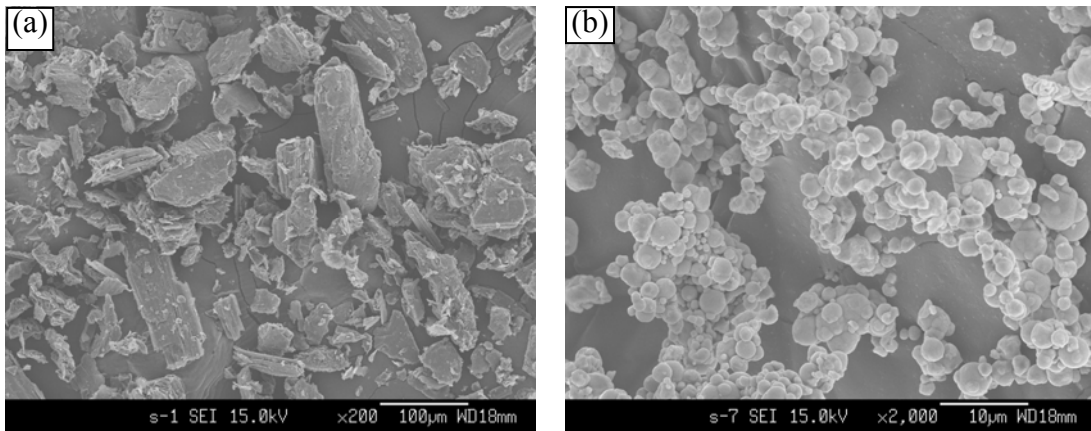


Fig. 1 SEM images of as-received (a) graphite and (b) iron powders.

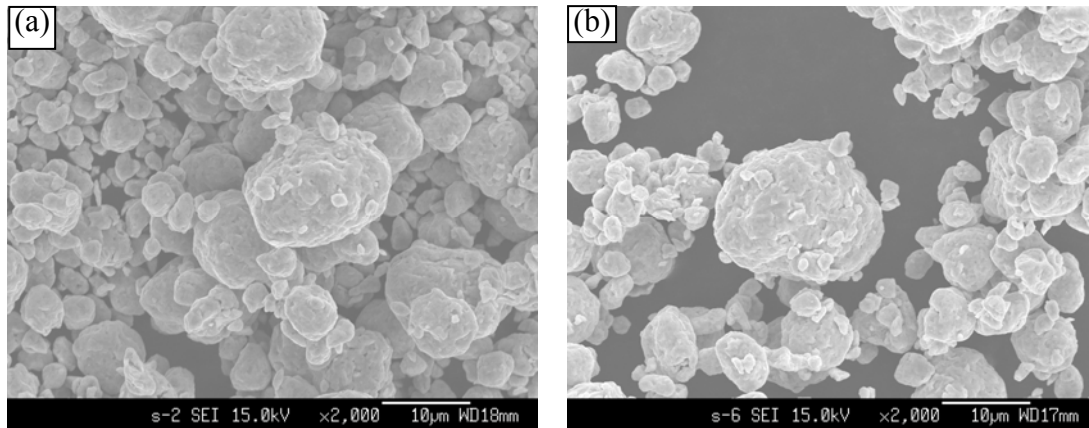


Fig. 2. SEM images of (a) Fe-0.4C and (b) Fe-0.6C powders mixtures MAed for 300 h.

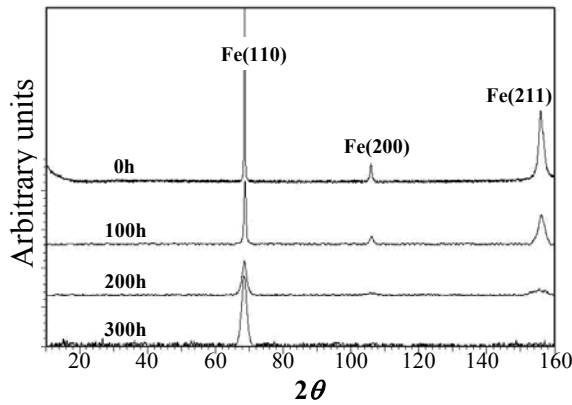


Fig. 3. XRD patterns of Fe-0.6C powders MAed for various time.

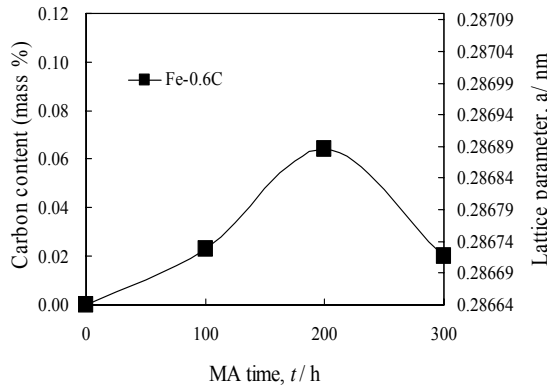


Fig. 4. Changes in carbon content and iron lattice parameter as a function of MA time

Figure 5 shows DTA-TG curves of Fe-0.4C and Fe-0.6C powders MAed for 200 h. The mass of the MAed powders increases slightly with heating temperature up to 500°C (see the TG curves). This suggests that the oxidation of iron occurs during the heating process due to the

impurity of atmosphere gas (Ar). With further heating, the mass decreases because of the oxidation of amorphous carbon to form CO or CO<sub>2</sub> gases. On the other hand, from DTA curves, it can be seen that exothermic peaks at about 370°C are caused by transformation of super-saturated iron solid solution and Fe/C amorphous phase into ferrite and carbide (Fe<sub>5</sub>C<sub>2</sub>) [8], [9]. It is confirmed that the intensity for these exothermic peaks decrease significantly for the powders MAed for 300 h because the transformation from the super-saturated iron solid solution and amorphous Fe/C to carbide occurs during MA as mentioned previously. The Fe<sub>5</sub>C<sub>2</sub> carbide transforms into the more stable Fe<sub>3</sub>C carbide (cementite) with further heating process up to 530°C.

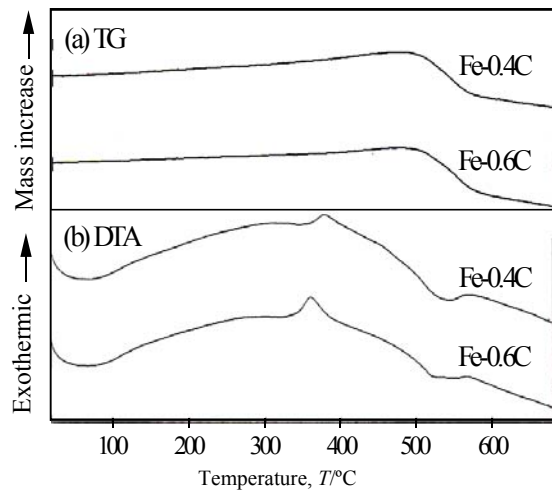


Fig. 5. DTA-TG curves of Fe-0.4C and Fe-0.6C powders MAed for 200h.

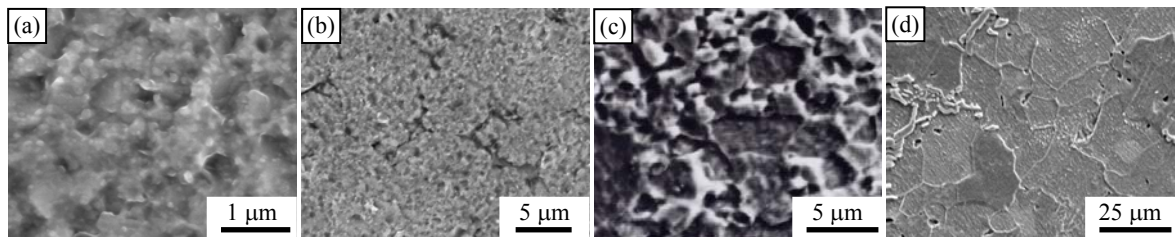


Fig. 6. SEM images of the Fe-0.6C compacts HPed at (a) 610°C with high magnification, (b) 610°C with low magnification, (c) 730°C and (d) 800°C.

Figure 6 shows SEM images of the Fe-0.6C compacts HPed at various temperatures. At low HP temperature (610°C), the compacts compose of nano-structured grains (see Figure 6 (a)). However, due to the low temperature, the sintering does not progress well and many voids remain (see Figure 6 (b)). In the case of HP at a temperature near  $A_1$  (730°C) and above  $A_1$  (800°C), both compacts undergo well-sintering process and have almost no voids. Many fine cementite precipitates in the ferrite matrix (Figure 6 (c)). In thermal refining standard steels, such structure is called sorbite. In compacts HPed at 730°C (see Figure 6 (c)), the ferrite grain size is small (about 2.3  $\mu\text{m}$ ) showing that the precipitation of fine cementite retards the growth of ferrite grain during the HP process. In the case of HP at 800°C, the sintering progresses well and the coarsening of ferrite grain takes place. Thus the ferrite grain size is large (about 17.4  $\mu\text{m}$ ) as shown in Figure 6 (d) and large cementite precipitates at grain boundaries. This structure is similar to that in annealed carbon steel, which is formed by transformation of austenite into ferrite and cementite during the cooling process. There is no significant difference between the microstructures of the Fe-0.4C and Fe-0.6C compacts.

Figure 7 shows the nominal stress-strain curves of tensile test for Fe-0.4C HPed compacts. Where A, B and C are HPed at 610, 730 and 800°C, respectively. No fracture strain is observed in the compact HPed at 610°C (a temperature below  $A_1$ ), showing that the specimen undergoes a brittle fracture. At a temperature near  $A_1$  (730°C), the strength increases abruptly up to 934 MPa and the fracture strain is about 0.12. However, no yield point is observed. With further temperature increase, at 800°C (above  $A_1$ ), the fracture strain increases significantly up to 0.28 and the yield point appears clearly. However, the tensile strength decreases rapidly (about 492 MPa).

Figure 8 shows the SEM images of the cross section of the fracture surface of the Fe-0.4C compacts HPed at various temperatures after tensile test. In the case of HP at 610°C, the fracture surface consists of many small brittle facets, indicating that the sintering process does not progress well because of the low sintering temperature (below  $A_1$ ). Therefore, the fracture occurs before the yield point and the fracture strain is almost zero. Such brittle fracture is not observed in both specimens HPed at 730 and 800°C. Small and large dimples are ob-

served in the fracture surface of both specimens. However, the dimple size in the specimen HPed at 800°C is larger than that at 730°C, resulting in the increase in fracture strain (see Figure 7). This is because, the enhancement of the sintering process, precipitation of large cementites and ferrite grain coarsening occur during HP. However, the tensile strength is far lower compared to that at 730°C. On the other hand, specimen HPed at 730°C has the highest tensile strength (934 MPa) and hardness (257 HV). This is because fine cementites are dispersed into relatively small ferrite grain.

Figures 9 shows the relationship between tensile strength and elongation, while Figure 10 shows the relationship between Vickers hardness and tensile strength of the HPed compacts. A range of data of standard (JIS) carbon steels through normalizing and thermal refining [15] are also given in these figures. The relationships of the compacts HPed at 730°C (near  $A_1$ ) and 800°C (above  $A_1$ ) are almost in agreement with those of standard steels. This is because the compacts have microstructures similar to those of thermal refined steels and normalized steels, respectively. Thus, MA and subsequent HP (consolidation) is a new technique of near net-shape to gain steels with excellent mechanical properties without thermal refining and addition of alloying elements.

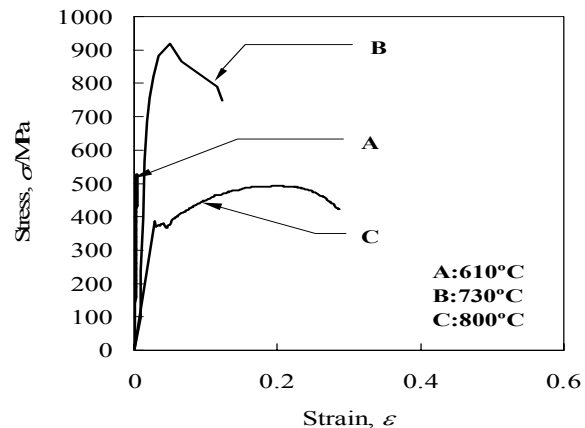


Fig. 7 Stress-strain curves of tensile test for Fe-0.4C HPed compacts.

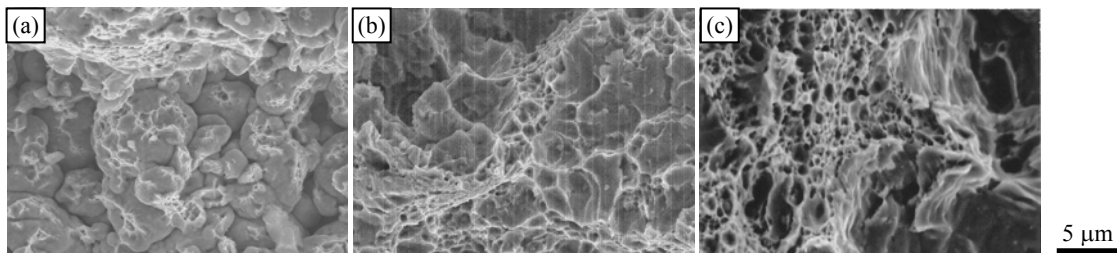


Fig. 8. SEM images of the cross section of the fracture surface of the Fe-0.4C compacts HPed at (a) 610, (b) 730 and (c) 800°C after tensile test.

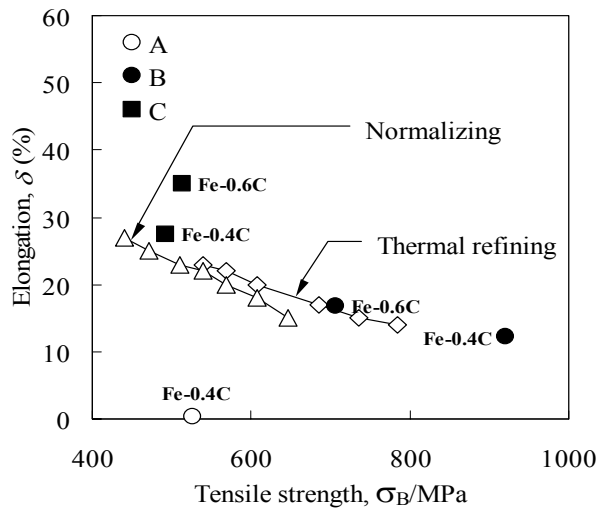


Fig. 9. Relationship between tensile strength and elongation of the HPed compacts

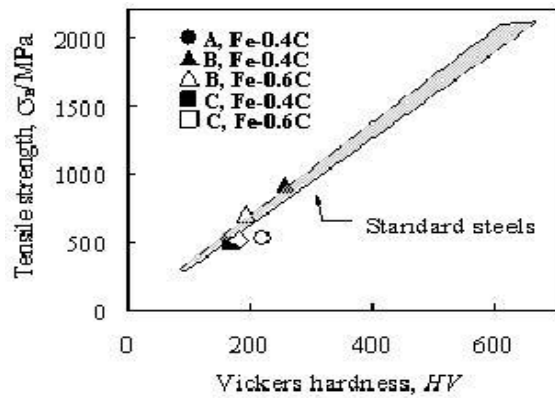


Fig. 10. Relationship between tensile strength and Vickers hardness of the HPed compacts

IV. CONCLUSION

During MA, refinement of crystallite, formations of super-saturated iron solid solution and Fe/C amorphous phase occurred first. With further MA time, these phases began to transform to more stable phases such as carbides. In the case of HP at 610°C (below  $A_1$ ), very fine cementites were precipitated in fine ferrite grain with sub-micron meter in the size. However, the mechanical properties could not be attained because of low sinterability. At 730°C (near  $A_1$ ), the strength

reaches the maximum value. With further temperature increase (at 800°C), the sintering progressed well and the coarsening occurred, resulting the decrease in the strength. However, the fracture strain increases significantly. The steels obtained in the present study had mechanical properties that were comparable to those of standard (JIS) steels through the well-established heat treatment such as normalizing and thermal refining.

V. REFERENCES

- [1] Koch C.C., Cavin O. B., Mckamey C. G., And Carbrough J.O., "Preparation of amorphous Ni[sub 60]Nb[sub 40] by mechanical alloying." *Appl. Phys. Lett.*, 43, 1017. 1983.
- [2] Schwarz R. B., Petrich R. R. And Saw K. R., "The synthesis of amorphous Ni-Ti alloy powders by mechanical alloying." *J. Non-Cryst. Solids*, 76, 281-302. 1982.
- [3] Eckert J., Holzer J. C., And Johnson W. L., "Thermal stability and grain growth behavior of mechanically alloyed nanocrystalline Fe-Cu alloys." *J. Appl. Phys.* 73, 131. 1993.
- [4] Gaffet E., Abdellaoui M. And Malhouroux-Gaffet M., "Formation of nanostructural materials induced by mechanical processings." *Materials Transactions, JIM*, 36 (2) 198-209. 1995.
- [5] Tanaka T., Nasu S., Ishihara K. N. And Shingu P. H., "Mechanical Alloying of Cast Iron Powders." *J. Japan Foundrymen's Society*, 65 (1) 19-24. 1993.
- [6] Matteazzi P. And Caer G. L., "Room-Temperature Mechano-synthesis of Carbides by Grinding of Elemental Powders." *J. Am. Ceram. Soc.*, 74, 1382-1387. 1991.
- [7] Kimura Y., Takaki S. And Goto H., Ultra Grain Refining of Iron Using Mechanical Milling Technique. *Powder and Powder Metallurgy*, 43, 584. 1996.
- [8] Nurul T. R., Kawamoto K., Sueyoshi H., Nakamura Y. And Nishida T., "Preparation of High Carbon System Alloy by Mechanical Alloying." *J. Japan Soc. Heat Treatment*, 39, 312-317. 1999.
- [9] Tanaka T., Nasu S., Ishihara K. N. And Shingu P. H., "Mechanism of Fe<sub>3</sub>C Formation by Mechanical Alloying." *J. Japan Foundrymen's Society*, 65 (1) 25-30. 1993.
- [10] Tanaka T., Nasu S., Ishihara K. N. And Shingu P. H., "Mechanical Alloying of the High Carbon Fe-C System." *J. Less-Common Met.*, 171, 237. 1991.
- [11] Le Caer And Matteazzi, 1991. Mössbauer Study of Mechano-synthesized Iron Carbides. *Hyperfine Interactions*, 66, 309-318. 1991.
- [12] Campbell S. J., Wang G. M., Calka A. And Kaczmarek, "Ball Milling of Fe<sub>75</sub>-C<sub>25</sub> Formation of Fe<sub>3</sub>C And Fe<sub>7</sub>C<sub>3</sub>." *Mat. Sci. and Eng.*, A226-228, 75-79.
- [13] Fasiska E. J. And Wagenblast H., "Elastic Constants of Binary Iron-Base Alloys." *Trans. Metallurgical Society of AIME*, 239, 1818-1820. 1967.